

# Computational studies of the bulk cobalt pentlandite ( $\text{Co}_9\text{S}_8$ ): Validation of the potential model

M.A. Mehlape<sup>1</sup>, P.E. Ngoepe<sup>1</sup> and S.C. Parker<sup>2</sup>

<sup>1</sup>Materials Modelling Centre, School of Physical and Mineral Sciences, University of Limpopo, South Africa, Private Bag, X1106, SOVENGA, 0727

<sup>2</sup>Computational Solid State Chemistry, University of Bath, Claverton Down, Bath, Avon, UK, BA2 7AY.

Email:mofuti.mehlape@ul.ac.za


**Abstract.** We use the density functional theory to study the cobalt pentlandite mineral ( $\text{Co}_9\text{S}_8$ ). We investigate various forms of the cobalt pentlandite,  $\text{Co}_9\text{S}_8$ , at different temperatures, using classical atomistic simulation methods with the support of electronic structure calculations. The first interatomic potentials of  $\text{Co}_9\text{S}_8$  based on the Born model, were derived with input data such as structure and elastic properties from experiments and electronic structure calculations respectively. The interatomic potentials were validated by running energy minimization and molecular dynamics calculations. The structure and elastic properties corresponded well with those determined by electronic structure methods. The calculations further reproduced the complex high temperature transformation to high form pentlandite and the melting of  $\text{Co}_9\text{S}_8$ ; as deduced from the crystal structure and radial distribution functions.

## 1. Introduction

Pentlandites,  $(\text{Fe}, \text{Ni}, \text{Co})_9\text{S}_8$ , are important nickel and cobalt sulphide minerals in economic deposits where it occurs with pyrrhotite, chalcopyrite and pyrite in mafic and ultramafic igneous rocks [1]. Furthermore, pentlandite minerals play an important role in the production of cleaner fuels with low or ultra-low sulphur content that require a continuous improvement of catalytic materials used in the refinement industry. In addition to supplying base metals, pentlandite compounds occur as solid solutions, in Merenksy reef, and intergrowths in UG2 reefs, with precious metal compounds, where the former occur in larger quantities [2]. In order to extract the precious metals from the ores effectively it is necessary to study and understand structural, including surface properties, of pentlandites in detail. Notwithstanding their significance in mineralogy, previous experimental studies on pentlandites are not as abundant as those of pyrites and metal oxide minerals, and computational modelling investigations are also very scarce. We present the first classical interatomic potential model [3] of  $\text{Co}_9\text{S}_8$ , and its validation, since the compound is easier to handle than  $(\text{Fe}, \text{Ni})_9\text{S}_8$ , owing to its cubic symmetry. Such potentials render structural studies of surfaces and nanoparticles, with large number of atoms, and their variation with temperature more amenable.

### 2.1. Cobalt Pentlandite, $\text{Co}_9\text{S}_8$ structure

The conventional unit cell of the cobalt pentlandite has the formula  $\text{Co}_{36}\text{S}_{32}$  and contains a cubic close-packed arrangement of sulphide ions containing 64 tetrahedral holes and 32 octahedral holes. Of the 64 tetrahedral holes, 32 are occupied by  $\text{Co}^{2+}$  ions, these being distributed through the lattice in groups of eight which lie at the corners of sub-cubes of edge length 0.250 nm. Of the 32 octahedral holes, 28 are pseudo-octahedral, distorted, and empty, whereas four are truly octahedral and each contains a Co atom in a formally zero oxidation state. Thus the solid attains the overall stoichiometry  $\text{Co}_9\text{S}_8$  [4]. Figure 1 shows the conventional unit cell of  $\text{Co}_9\text{S}_8$ . The  $\text{Co}_9\text{S}_8$  has a space group  $Fm\bar{3}m$ .

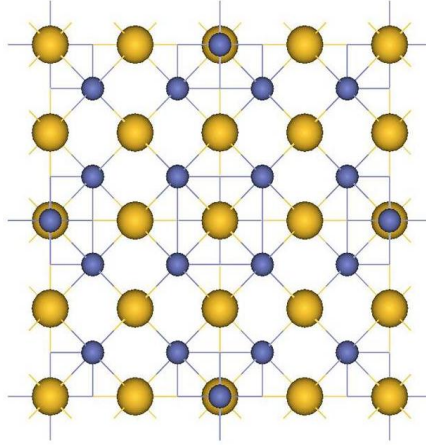

**Figure 1:** Conventional unit cell of cobalt pentlandite structure ( $\text{Co}_9\text{S}_8$ ). Blue and yellow spheres represent cobalt (Co) and sulphur (S) atoms respectively.

## 2. Methodology

The VASP code [5] was used to calculate the elastic properties of  $\text{Co}_9\text{S}_8$  (used as the existing data, for derivation of the interatomic potentials). Interatomic potentials of  $\text{Co}_9\text{S}_8$  were derived by GULP [6] code and together with DLPOLY [7] molecular dynamics (MD) simulations were performed. The Born ionic model [8] was used and parameters were derived for short range interactions represented by the Buckingham potential, Morse potential and three body terms:

### *Buckingham Potential*

In the Buckingham potential, the repulsive term is replaced by an exponential term and potential takes the form

$$U(r_{ij}) = A_{ij} * \exp^{-r_{ij} / \rho_{ij}} - \frac{C_{ij}}{r_{ij}^6} \quad (1)$$

where  $A_{ij}$  and  $\rho_{ij}$  are parameters that represent the ion size and hardness, respectively, while  $C_{ij}$  describe the attractive interaction and  $r_{ij}$  is the distance between ion  $i$  and ion  $j$ . The first term is known as the Born-Mayer potential and the attraction term (second term) was later added to form the Buckingham potential. Very often, for the cation-anion interactions, the attractive term is ignored due to the very small contribution of this term to the short-range potential, or, alternatively, the interaction is subsumed into the  $A$  and  $\rho$  parameters.

### *Morse Potential*

The Morse potential is used to model the interactions between covalently bonded atoms and has the form

$$U(r_{ij}) = A_{ij} * (1 - \exp^{-B_{ij} * (r_{ij} - r_0)})^2 - A_{ij} \quad (2)$$

where  $A_{ij}$  is the bond dissociation energy,  $r_0$  is the equilibrium bond distance, and  $B_{ij}$  is a function of the slope of the potential energy well. The Coulombic interactions between covalently bonded atoms are often partially or totally ignored as the Morse potential already contains the attractive component of the interaction between neighbours.

### *Three-Body Potential*

A further component of the interactions of covalent species is the bond-bending term, which is added to take into account the energy penalty for deviations from the equilibrium value. Hence, this potential describes the directionality of the bonds and has a simple harmonic form:

$$U(\theta_{ijk}) = \frac{1}{2} k_{ijk} (\theta_{ijk} - \theta_0)^2 \quad (3)$$

where  $k_{ijk}$  is the three-body force constant,  $\theta_0$  is equilibrium angle and  $\theta_{ijk}$  is the angle between two interatomic vectors  $i - j$  and  $j - k$ .

### 3. Results and Discussions

The properties, i.e. lattice parameters and elastic properties to validate the derived potential model of  $\text{Co}_9\text{S}_8$  are discussed and also molecular dynamics simulation of bulk  $\text{Co}_9\text{S}_8$  at high temperatures is discussed.

#### 3.1. Validation of Potential Model of $\text{Co}_9\text{S}_8$

The accuracy of the derived interatomic potentials was checked by comparing the known experimental and calculated data. To validate our potential models we start by showing the properties that were obtained from our derived potentials i.e., lattice parameters and elastic properties. The lattice parameter obtained using energy minimisation code GULP is in good agreement with those from the literature as shown in Table 1.

**Table 1.** Comparison of the lattice parameter of  $\text{Co}_9\text{S}_8$ , obtained from the derived interatomic potentials, with the other calculated and experimental values.

Method	a (Å)
GULP (This work)	9.806
VASP (PW-GGA)(This Work)	9.811
*TB-LMTO <sup>a</sup>	9.918
Extended Huckel Type Band Calculations <sup>b</sup>	9.927
EXPERIMENTAL <sup>c</sup>	9.928

<sup>a</sup>[10], <sup>b</sup>[11], <sup>c</sup>[9]

\*Tight-binding linear-muffin-tin-orbital

Table 2 shows a comparison of the elastic properties of  $\text{Co}_9\text{S}_8$  we calculated using DFT methods (VASP code) and those calculated from our derived interatomic potentials employing the GULP code; experimental elastic constants are currently not available for  $\text{Co}_9\text{S}_8$ . The elastic constants from the interatomic potentials are in good agreement with those from DFT calculations, together with the various moduli of elasticity, i.e. the bulk, shear, elasticity moduli and Poisson's ratio. In addition, the  $\text{Co}_9\text{S}_8$  phase has elastic constants that satisfy the generalized elastic stability criteria for cubic crystals [12], [13];

$$(C_{11} - C_{12})/3 > 0, C_{11} + 2C_{12} > 0, C_{44} > 0 \quad (4)$$

The bulk modulus  $B$ , shear modulus  $G$  and elastic modulus  $E$  of the cubic  $\text{Co}_9\text{S}_8$  phase were deduced according to the following formulae [14], [15], [16], [17];

$$B = \frac{1}{3}(C_{11} + 2C_{12}) \quad (5)$$

$$G = \frac{1}{5}(C_{11} - C_{12} + 3C_{44}) \quad (6)$$

$$E = \frac{(C_{11} - C_{12} + 3C_{44})(C_{11} + 2C_{12})}{2C_{11} + 3C_{12} + C_{44}} \quad (7)$$

Poisson ratio  $\nu$  is obtained from:

$$\nu = \frac{3B - E}{6B} \quad (8)$$

**Table 2.** Calculated elastic constants and moduli of the  $\text{Co}_9\text{S}_8$  phase


Properties	VASP	GULP (Fitted)
$C_{11}$	223.8	214.3
$C_{12}$	80.3	82.3
$C_{44}$	71.3	70.0
Bulk Modulus, $B$ (GPa)	128.1	126.3
Shear Modulus, $G$ (GPa)	71.5	68.4
Elastic Modulus, $E$ (GPa)	180.8	173.8
Poisson Ratio, $\nu$	0.26	0.27
Volume ( $\text{\AA}^3$ ) *		947.6

\*Experimental Volume is  $978.56 \text{ \AA}^3$  [9]

### 3.2. Molecular Dynamics Simulation of $\text{Co}_9\text{S}_8$

In order to demonstrate the phase changes of the  $\text{Co}_9\text{S}_8$  structure using molecular dynamics, we superimposed the total radial distribution functions of  $\text{Co}_9\text{S}_8$  bulk at different temperatures in Figure 2. The total magnified RDFs indicate that as the temperature increases, the peaks become broader and the number of peaks decreased. Furthermore, the total RDFs show that between 300 and 900 K, the second and third peaks (denoted by B and C, respectively) are well-defined and approach each other. However, at 1100 K the peaks coalesce, and the combined peak (denoted by D) remains in the same position at 1300 K. This is the temperature range where  $\text{Co}_9\text{S}_8$  undergoes phase change from normal to high form pentlandite according to experimental work of Kitakaze & Sugaki [18]. They reckoned that the high form of cobalt pentlandite is stable up to  $930^\circ \pm 3^\circ \text{C}$  ( $1203 \text{ K} \pm 3 \text{ K}$ ), where it breaks down to a mixture of cobalt monosulfide (Fe- and Ni-free end-member of monosulfide solid-solution) and liquid in an incongruent melting reaction. They finally observed that remnant cobalt monosulfide melts completely at  $1069^\circ \pm 5^\circ \text{C}$  ( $1342 \pm 5 \text{ K}$ ). Indeed our simulations (Figure 2) confirm the molten phase at 1500 K, since the height of the coalesced peak is reduced. At a higher temperature of 1900 K the height of the coalesced peak is further reduced showing a completely molten structure. The first peak of the RDF gives a radial distance of approximately  $2.15 \text{ \AA}$  at 300 up to 900 K and  $2.17 \text{ \AA}$  at 1100 K up to 1500 K. The radial distance is close to the experimental interatomic distance of Co-S on

the tetrahedral site which is 2.13 Å. The second and third peaks give approximately 3.45 Å and 3.97 Å, respectively at 300 K up to 900 K. At 1100 K up to 1500 K the second and third peaks combine to give one peak of approximately 3.61 Å. The radial distance is close to the EXAFS measurement interatomic distance of Co-Co on the tetrahedral site which is 3.54 Å [18]. Hence it may be deduced that the phase change from the normal to high form pentlandite is associated with the movement of Co on the tetrahedral sites. The ability of the interatomic potentials to reproduce the complex high temperature phase change of pentlandite and to elucidate atoms participating in such change demonstrates the robustness of the potentials.

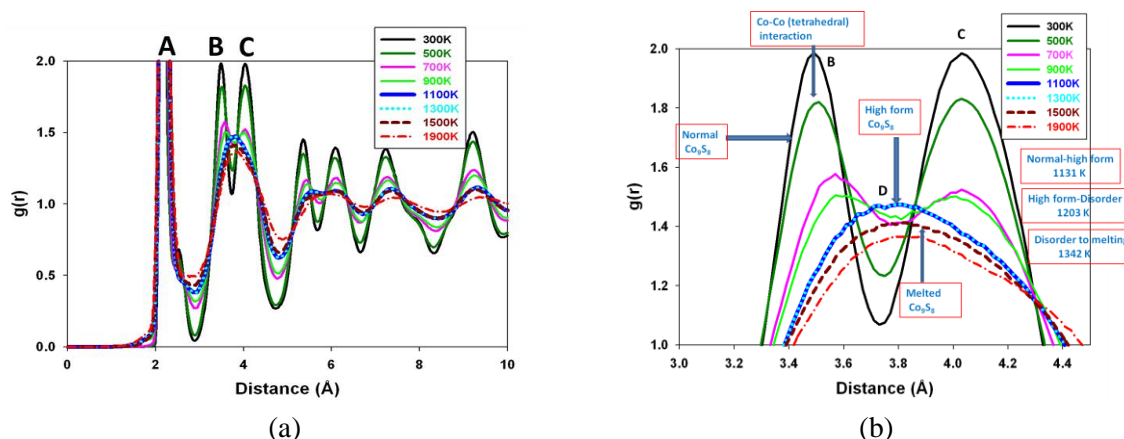

**Figure 2:** The total radial distribution functions of the  $\text{Co}_9\text{S}_8$  bulk structure at (a) different temperatures and (b) magnified RDFs showing the coalescing of the adjacent Co-Co tetrahedral peaks.

#### 4. Conclusion

The derived interatomic potentials of  $\text{Co}_9\text{S}_8$  were validated by the accurate determination of structure and elastic constants. The robustness of the interatomic potentials was further illustrated by their ability to reproduce complex high temperature transitions of the bulk  $\text{Co}_9\text{S}_8$  which were observed experimentally. The change of radial distribution functions (especially the coalescing (coming together) of the adjacent Co-Co tetrahedral peaks) deduced from molecular dynamics studies, depicted the phase change from the normal to the high form Co pentlandite above 1100 K.

#### Acknowledgements

The computations were performed at the Materials Modelling Centre (MMC), University of Limpopo and at the Centre for High Performance Computing (CHPC). We also acknowledge the National Research Foundation (NRF) and Anglo Platinum for funding.

#### References

- [1] Borodaev Y S, Bryzgalov I A, Mozgova N N and Uspenskaya T Y 2007 *Moscow Univ. Geol. Bull.* **62** 85-97
- [2] Johan Z, Ohnenstetter M, Slansky E, Barron L M and Suppel D 1989 *Mineralogy and Petrology*, **40** 289-309
- [3] Mehlae M A, 2013 *Computational Modelling Studies of Cobalt Pentlandite ( $\text{Co}_9\text{S}_8$ )*. (Ph Thesis, University of Limpopo)
- [4] Hoodless R C, Moyes R B and Wells P B 2006 *Catalysis Today*, **114** 377–382
- [5] Kresse G and Hafner J 1993 *Phys. Rev. B* **47** 558–561
- [6] Gale J D 1997 *J. Chem Soc. Faraday Trans.* **93** 629
- [7] Smith W and Forester T R 1996 *J. Mol. Graphics*, **14** 136-341
- [8] Born M and Huang K 1954 *Dynamical Theory of Crystal Lattices 1st edition* (University Press: Oxford)
- [9] Geller S 1962 *Acta Crystallogr.* **15** 1195-1198
- [10] Chauke H R, Nguyen-Manh D, Ngoepe P E, Pettifor D G and Fries S G 2002 *Phys. Rev. B*,

- [11] Burdett J K and G J Miller 1987 *J. Amer. Chem. Soc.* **109** 4081-91
- [12] Yu W, Wang N, Xiao X, Tang B, Peng L and Ding W 2009 *Solid State Sciences*, **11** 1400–07
- [13] Dian-wu Z, Jin-shui L and Ping P 2011 *T. Nonferr. Metal. Soc.* **21** 2677–83
- [14] Mehl M J, Osburn J E, Papaconstantopoulos D A and Klein B M 1990 *Phys. Rev. B: Condensed Matter*, **41** 10311–23
- [15] Wang T, Chen P, Deng Y and Tang B, 2011 *Trans. of Nonferr. Metal Soc. of China*, **21** 388–394
- [16] Screiber E, Anderson O L and Soga N, 1973 *Elastic constants and their measurement*, (McGraw Hill, New York)
- [17] Benkabou F, Aourag H and Certier M, 2000 *Mater. Chem. Phys.* **66** 10–16
- [18] Kitakaze A and Sugaki A 2004 *Can. Mineral*, **42** 17-42
- [19] Bouwens S M A M, Van Veen J A R, Koningsberger D C, De Beer V H J, and Prins R, 1991 *J. Phys. Chem.* **95** 134-139