

Modified hummers synthesis and structural characterisation of graphene oxide

MW Makgoba¹, TE Mosuang¹ and G Ndlovu²

¹Department of Physics, University of Limpopo, Private Bag x1106, Sovenga, 0727, Limpopo Province, South Africa.

²Advanced Materials Division/MINTEK, Private Bag X3015, Randburg 2125, Gauteng Province, South Africa.

makgoba.walter@gmail.com, amos.akande@ul.ac.za

Abstract. Graphene oxide (GO) was synthesised using modified hummers method. X-Ray Diffraction (XRD), Scanning Electron Microscopy (SEM), Transmission Electron Microscopy (TEM), Fourier Transform Infrared Spectroscopy (FTIR), Raman Spectroscopy (RM) and Atomic Force Microscopy (AFM) was utilised to acquire the structural properties of GO. Each spectroscopic technique reveals unique features about the surface morphology of graphene oxide. XRD confirmed the crystalline nanosheets stacking of a carbon honeycomb. SEM and TEM revealed wrinkles and folding of planar honeycomb layers. FTIR and RM indicated the presence of carbonyl, alkoxy, epoxy, and hydroxyl functional groups. AFM further confirmed the surface roughness and the thickness of GO layer.

1. Introduction

Graphene oxide (GO) is a new interesting material which is derived from graphene and the oxygen functional group(s) [1]. GO is known to possess some interesting properties such as high surface area, high mechanical stiffness, high Young's modulus and exceptional thermal conductivity [2-3]. Due to these properties GO has attracted enormous great research interest. Nowadays, the synthesis and modification of GO has been one of the major focus and interesting part of graphene related research. The structure of graphene oxide can be defined as a layer of graphene with a number of oxygen functional group(s), such as hydroxyl (OH), epoxy (C-O), carbonyl (C=O) and alkoxy (C-O-C) distributed on the graphene surface [4]. GO is a promising material for future technologies due to the oxygen functional group as well as their minute size and shape [5]. This material has been identified as a potential candidate for advanced semiconducting applications such as water treatment as well as gas sensing [1].

The presence of the oxygen containing functional groups in GO influence this material's hydrophilic behaviour and its polar nature, as a results of which GO can be easily dispersed in several solvents such as water [6], in the process gaining advantage in terms of other peculiar properties over its precursor graphene. These functional groups highlight the opportunities for surface modification in GO which is very much suitable for nanocomposite materials.

This paper is focused on the synthesis and structural characterisation of graphene oxide. Accordingly, the synthesis of graphene oxide is more favourable over other graphene materials due to its low cost, easy access and its ability to be easily converted to graphene [7]. Graphite which is defined as a packed layers of graphene is the main source of graphene oxide [8]. GO has been synthesised using modified hummers method and was further characterised using various spectroscopic instruments including X-

Ray Diffraction (XRD), Scanning Electron Microscopy (SEM), Transmission Electron Microscopy (TEM), Fourier Transform Infrared Spectroscopy (FTIR), Raman Spectroscopy (RM), and Atomic Force Microscopy (AFM).

2. Materials and Methods

2.1 Reagents used for the synthesis of graphene oxide

The materials used in this study were purchased from Sigma Aldrich. The materials are: graphite (99% purity), sodium nitrate (99% NaNO₃), potassium permanganate (99% KMnO₄) and sulphuric acid (98% H₂SO₄), hydrogen peroxide (50% H₂O₂), hydrochloric acid (35% HCl).

2.2 Synthesis of graphene oxide

The modified hummers method was used to synthesise graphene oxide (GO) [9]. This method involves the treatment of graphite flakes with a mixture of sodium nitrate (NaNO₃), potassium permanganate (KMnO₄) and sulphuric acid (H₂SO₄). During the synthesis of GO, 120 ml of concentrated H₂SO₄ was measured and cooled to the temperature below 5 °C in an ice bath. In the process 2.5 g of NaNO₃ and 2 g of graphite were slowly added to the H₂SO₄. The mixture was then allowed to stir for a maximum of 30 min under an ice bath at 300 rpm (revolution per minutes). 15 g of KMnO₄ was then added slowly to the mixture after 30 min with continuous stirring at 300 rpm. The temperature of the mixture was always kept below 5 °C. After KMnO₄ was successfully stirred into the mixture, the ice bath was replaced with an oil bath. The temperature of the mixture was increased and maintained in the range of 60 - 70 °C in the oil bath. The mixture was further allowed to stir for extra 30 min at 300 rpm. Furthermore, after 30 min of stirring, the mixture was then allowed to react whilst stirring for 24 h under room temperature in the oil bath still at 300 rpm.

After the full complete 24 h reaction, the mixture was cooled to a temperature below 5 °C in an ice bath, followed by gradual addition of 220 ml of de-ionized water drop by drop wise in the mixture to increase the temperature to 55 °C maximum while stirring at 300 rpm. Subsequent the gradual addition of 220 ml of de-ionized water, the mixture was further heated in an oil bath and refluxed for 24 h at a temperature below 60 °C. The mixture was then cooled to room temperature and 50 ml of hydrogen peroxide (H₂O₂) was slowly added to eliminate excess of KMnO₄. The exothermic reaction occurred during the addition of H₂O₂ and the mixture changed to bright yellow. The mixture was then filtered and the obtained product (graphite oxide) was washed continuously with 0.1 M of hydrochloric acid (200 ml) to remove the metal ions. The graphite oxide was further washed with the de-ionized water for several times using centrifuge, until the pH value of the supernatant was approximately close to the pH of the water. Then, the graphite oxide was dried up in a vacuum oven at a temperature of 60 °C for 24 h. Finally, 5 mg of graphite oxide was exfoliated by sonication in a 100 ml of deionized water to yield several graphene oxide nanosheets.

2.3 Characterization of graphene oxide

X-ray diffraction pattern of GO was conducted using Bruker D2 Phaser Diffractometer ($\lambda = 0.15418$ nm) which uses secondary graphite monochromated with CuK α radiation. The surface of GO was investigated using ZEISS SEM and Perkin Elmer TEM. The presence of the oxygen functional groups on the hexagonal honeycomb sheet was confirmed by Perkin Elmer FTIR TWO spectrometer at the spectral wavenumber range of 400 cm⁻¹ to 4000 cm⁻¹. Perkin Elmer Raman Spectrometer was used to analyse the structural characteristics of GO at a laser voltage of 50% with a beam exposure of 10 s. Images of GO layers were further explored and obtained using Veeco-nano scope AFM in a contact mode.

3. Results and Discussion

3.1 X-ray diffraction analysis

The x-ray diffraction spectrum confirms that GO crystallise into nanosheet form with a sharp peak at $2\theta = 11.1^\circ$ which corresponds to the interlayer spacing of 0.791 nm as depicted in figure 1. In addition,

the diffraction peak correspond with the (001) plane of GO. However, the x-ray diffraction of the well-ordered graphene usually depicts a sharp peak at $2\theta = 26.7^\circ$ [10]. This simply suggests that the sudden changes in the GO peak is due to the presents of the oxygen containing functional groups lying on the graphene surface. Commonly, the interlayer spacing of GO is known to range from 0.6 to 1.0 nm depending on the oxidation process involved during the synthesis procedure [11]. Therefore, since the obtained interlayer spacing for GO (0.791nm) lies between 0.6 and 1.0 nm, this shows that the synthesised GO is highly oxidized. The Bragg law [12] has been used in the determination of the interlayer spacing. The oxygen functional groups lying on the graphene sheets are also responsible for the increase in the interlayer spacing of GO [13]. The observed value for the sharp peak of GO approximately corresponds with the values reported in the literature [14]. The crystal size of this material was calculated to be 4.7 nm (47 Å). The Debye-Scherrer [15] equation was used to calculate the crystal size.

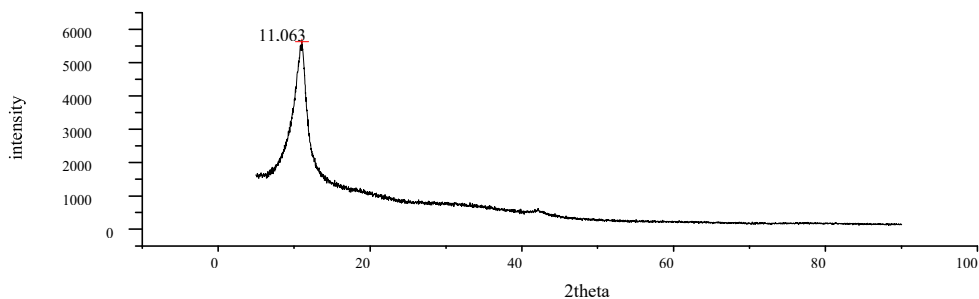


Figure 1. X-ray diffraction of GO.

3.2 Scanning and Transmission Electron Microscopy

The SEM micrograph suggests, the folding or piling of the layers with the surface morphology which is wrinkled, as shown in figure 2. This could be due to oxygen functional groups and other structural defects [16]. Based on the synthesis of GO by improved method, the wrinkles in GO are also caused by the folding of the GO sheets [17].

The TEM micrograph in figure 3 further shows evidence of the wrinkles in the middle of the GO nanosheets. The wrinkles further extend towards the edges. The same observations are noted and reported by Singh et al. [18]. It must be noted that the TEM image was taken in the bright field mode of the microscope where only transmitted electrons are allowed to pass through the aperture. The dark region at the middle and the edges of the GO nanosheets may be caused by the presence of wrinkles.

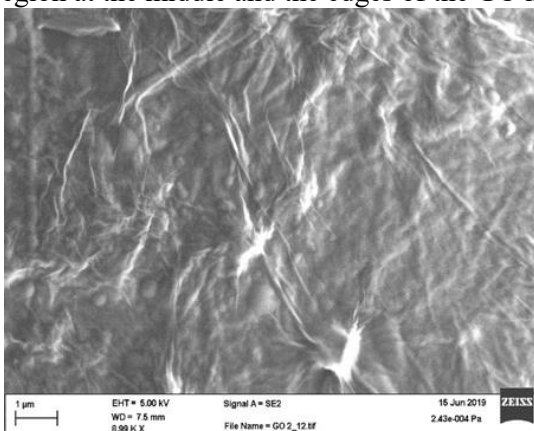


Figure 2: SEM micrograph of GO.

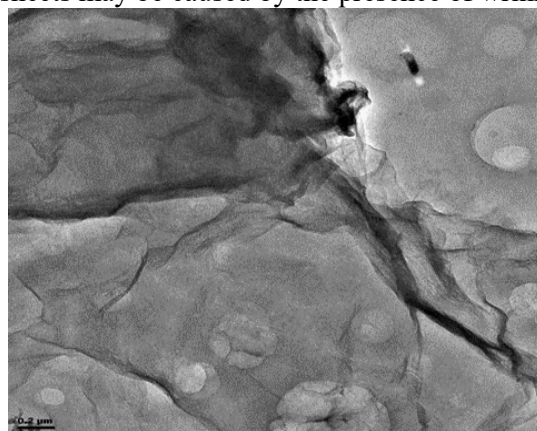


Figure 3: TEM micrograph of GO.

3.3 Fourier Transform Infrared Spectroscopy

In figure 4, the FTIR spectra of GO is shown. The spectra indicate the existence of various functional groups: hydroxyl (OH), carbonyl (C=O), epoxy (C-O), and alkoxy (O-C-O). The hydroxyl (OH) and carbonyl (C=O) groups stretching vibrations can be identified by the bands appearing at 3358 cm^{-1} and 1728 cm^{-1} respectively. Furthermore, the bands appearing at wavenumbers 1224 cm^{-1} and 1050 cm^{-1} correspond to epoxy (C-O) and alkoxy (O-C-O) stretching vibrations respectively. The obtained FTIR results are in good agreement with literature reports as outlined by Zhang et al. [19] and confirms the oxidation of graphite during the synthesis of GO via modified hummers method.

3.4 Raman Spectroscopy

According to many studies, the Raman spectra of graphene oxide usually exhibits two strong peaks, the D and the G peaks at approximately 1343 cm^{-1} and 1598 cm^{-1} respectively [20]. In this study, the D and the G peaks are observed at 1308 cm^{-1} and 1596 cm^{-1} respectively as illustrated in figure 5. The G-peak is usually because of the carbon-carbon bond stretching and the D-peak is associated with the presents of the oxygen functional groups on the graphene sheets [20]. If the intensity of the D peaks is (ID) and that of the G peak is (IG), the increase in the intensity of the ratio of the D and the G (ID/IG) peaks usually indicates the decrease in the average size of carbon-carbon bonds [21]. The ratio of the intensity of GO is 0.82 as compared to the theoretical value of 0.84, which suggests an increase in the average size of the carbon-carbon bonds stretching on the graphene sheets. Consequently, an increased aromaticity in the GO structure which is related with enlarged surface area and improved stability. As a results, Raman spectroscopy was successfully conducted to confirm the chemical changes in the graphitic structure.

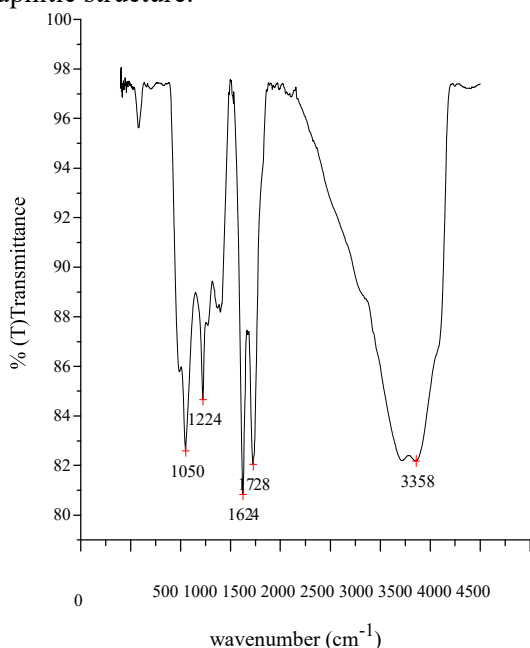


Figure 4. FTIR spectra of GO.

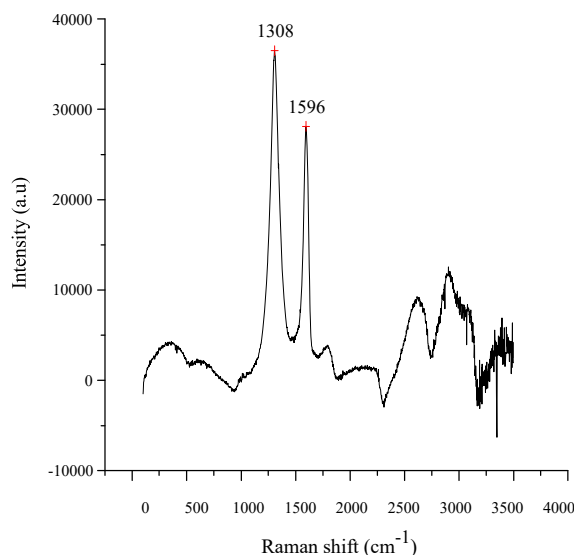


Figure 5. Raman Spectroscopy of GO.

3.5 Atomic Force Microscopy

Figures 6 and 7 shows that the AFM GO layers have different lateral sizes as well as different layer thickness. The folding or piling of the layers can also be observed which could have resulted when drying GO on the glass substrate as observed in figure 7. A typical height profile in figures 6 and 8 reveals the thickness of 2.993 nm of a single GO layer with the root mean square (RMS) value of the surface roughness of 1.134 nm due to the oxygen functional groups as reported in the literature. The thickness of graphene is approximated to range from 0.34 to 1.27 nm [22]. Therefore, since the obtained

thickness for GO (2.993 nm) is out of the approximated range of graphene, this could be attributed to the presence of the oxygen atoms laying on the graphene sheets causing the folding of GO nanosheets. As a result, GO is expected to be thicker than graphene because of the surface oxygen functional groups. However, this spectroscopic technique has difficulties in determining the exact number of layers in graphene and graphene oxide [23], hence this could also introduce difficulties in obtaining the exact thickness of GO.

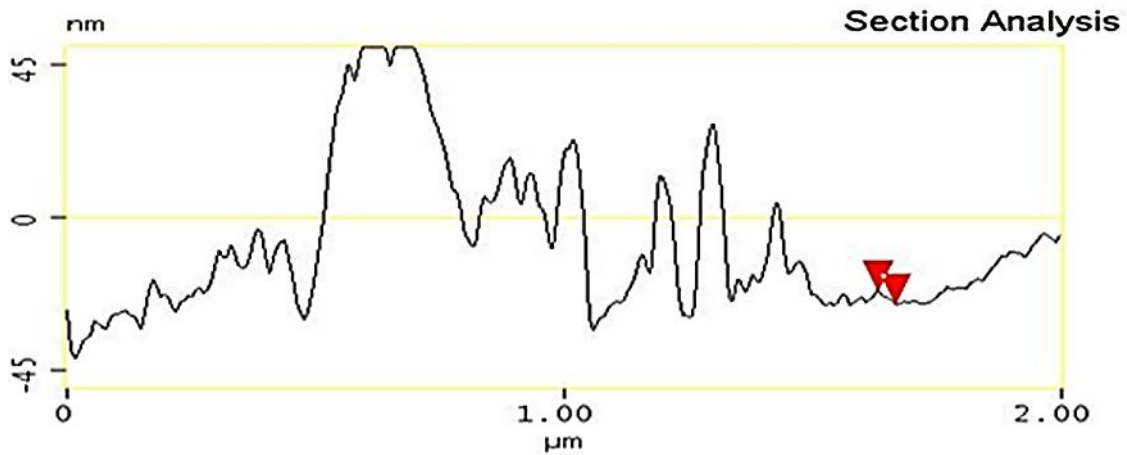


Figure 6: The sectional analysis of the GO nanosheets.

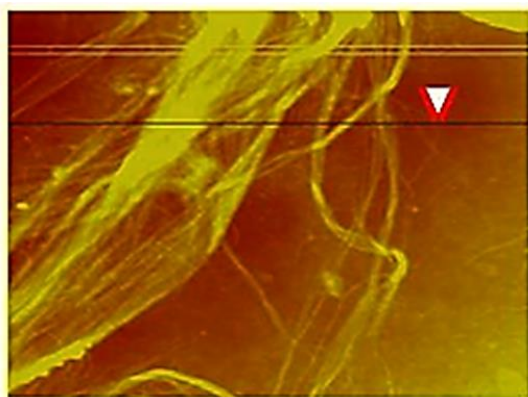


Figure 7: The AFM micrograph of GO nanosheets.

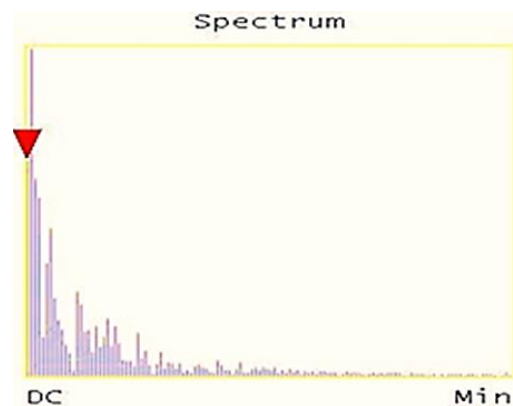


Figure 8: The spectral analysis of GO height profile.

4. Conclusion

Graphene oxide was successfully synthesised via modified hummers method. An acceptable interpretation of the surface morphology of graphene oxide through the spectroscopic instrument was successfully achieved. Correspondingly, SEM and TEM complement each other on the wrinkles and folding of the GO layers. The FTIR and RM results suggest the presence of the oxygen functional groups in the honeycomb sheets and AFM confirms that the synthesised GO is a nanomaterial with a rough surface due to the oxygen functional groups.

5. Reference

- [1] Chen H, Feng H and Li J 2012 *Chem. Rev* **112** 6027.
- [2] McAllister MJ, Li JL, Adamson DH, Schniepp HC, Abdala AA, Liu J, Herrera-Alonso M, Milius DL, Car R, Prud'homme RK and Aksay IA 2007 *Chem. Mater* **19** 4396.
- [3] Ramanathan T, Abdala AA, Stankovich S, Dikin DA, Herrera-Alonso M, Piner RD, Adamson DH, Schniepp HC, Chen X, Ruoff RS, Nguyen ST, Aksay IA, Prud'Homme RK and Brinson LC 2008 *Nat. Nanotechnol* **3** 327.
- [4] Raccichini R, Varzi A, Passerini S and Scrosati B 2015 **14** 271.
- [5] Huang X, Yin Z, Wu S, Qi X, He Q, Zhang Q, Yan Q, Boey F and Zhang H 2011 *Small* **7** 1876.
- [6] Pendolino F and Armata N Springer Briefs in Applied Sciences and Technology.
- [7] Bai H, Li C, Wang, X and Shi G 2011 *J. Phys. Chem. C* **115** 5545.
- [8] Brodie BC 1859 *Philosophical Transactions of the Royal Society of London* **149** 249.
- [9] W.S. Hummers WS and Offeman RE 1958 *J. Am. Chem. Soc.* **80** 1339.
- [10] Ashori A, Rahmani H and Bahrami R 2015 *Polym. Test.* **48** 82.
- [11] Ramesh P, Bhagyalakshmi, S and Sampath S 2004 *J. Colloid Interface Sci.* **274** 95.
- [12] Li J, Zeng X, Ren T, and Van Der Heide E 2014 *Lubricants* **3** 137.
- [13] Shen JF, Hu YZ, Shi M, Lu X, Qin C, Li C and Ye M.X 2009 *Chem. Mater* **21** 3514.
- [14] Ruiguang X and Yanan L.Y 2016 *Chem. Commun.*, **52** 390.
- [15] Fischer HE, Barnes AC and Salmon PS 2006 *Rep. Prog. Phys.* **69** 233.
- [16] Mungse HP and Khatri O.P 2014 *J. Phys. Chem. C* **118** 14394.
- [17] Yu H, Zhang B, Bulin C, Li R, and Xing R 2016 *Sci. Rep* **6** 36143.
- [18] Singh M, Kaushal S, Singh P and Sharma J 2018 *J. Photochem. Photobiol. A.* **364** 130.
- [19] Zhang L, Lu Z, Zhao Q, Huang J, Shen and Zhang Z 2011 *Small* **7** 460
- [20] Kudin KN, Ozbas B, Schniepp HC, Prud'homme RK, Aksay IA and Car R 2008 *Nano Lett.* **8** 36.
- [21] Dresselhaus MS, Dresselhaus G, Saito R and Jorio A 2005 *Phys. Rep.* **409** 44.
- [22] Li D, Muller MB, Gilje S, Kaner RB and Wallace GG 2008 *Nat. Nanotechnol.* **3** 101.
- [23] Liu WW, Chai SP, Mohamed AR and Hashim U 2014 *J. Ind. Eng. Chem.* **20** 171.